



GLOBAL JOURNAL OF RESEARCHES IN ENGINEERING  
CIVIL AND STRUCTURAL ENGINEERING  
Volume 12 Issue 2 Version 1.0 February 2012  
Type: Double Blind Peer Reviewed International Research Journal  
Publisher: Global Journals Inc. (USA)  
Online ISSN: 2249-4596 & Print ISSN: 0975-5861

# Interpretation of Rice Husk Ash on Geotechnical Properties of Cohesive Soil

By Grytan Sarkar, Md. Rafiqul Islam, Dr. Muhammed Alamgir, Dr. Md. Rokonuzzaman

*Khulna University of Engineering & Technology(KUET), Khulna, Bangladesh*

**Abstract** - This paper demonstrates the effects of rice husk ash (RHA) on the geotechnical properties of soil in stabilized forms specifically strength, workability, compaction and compressibility characteristics. Therefore, laboratory tests such as compaction, Atterberg limits, free swell index, unconfined compressive strength, direct shear and consolidation tests for different percentages of RHA content and original soil samples were performed. These test results show that the soil can be made lighter which leads to decrease in dry density and increase in moisture content and reduced free swelling and compressibility due to the addition of RHA with the soil. Besides that the unconfined compressive strength and shear strength of soil can be optimized with the addition of 10% RHA content.

**Keywords** : RHA, Index Properties, strength properties, swelling and consolidations.

**GJRE-E Classification** : FOR Code: 090501



*Strictly as per the compliance and regulations of:*



© 2012 Grytan Sarkar, Md. Rafiqul Islam, Dr. Muhammed Alamgir, Dr. Md. Rokonuzzaman. This is a research/review paper, distributed under the terms of the Creative Commons Attribution-Noncommercial 3.0 Unported License (<http://creativecommons.org/licenses/by-nc/3.0/>), permitting all non commercial use, distribution, and reproduction in any medium, provided the original work is properly cited.

# Interpretation of Rice Husk Ash on Geotechnical Properties of Cohesive Soil

Grytan Sarkar<sup>a</sup>, Md. Rafiqul Islam<sup>σ</sup>, Dr. Muhammed Alamgir<sup>p</sup>, Dr. Md. Rokonzaman<sup>σ</sup>

**Abstract** - This paper demonstrates the effects of rice husk ash (RHA) on the geotechnical properties of soil in stabilized forms specifically strength, workability, compaction and compressibility characteristics. Therefore, laboratory tests such as compaction, Atterberg limits, free swell index, unconfined compressive strength, direct shear and consolidation tests for different percentages of RHA content and original soil samples were performed. These test results show that the soil can be made lighter which leads to decrease in dry density and increase in moisture content and reduced free swelling and compressibility due to the addition of RHA with the soil. Besides that the unconfined compressive strength and shear strength of soil can be optimized with the addition of 10% RHA content.

**Keywords** : RHA, Index Properties, strength properties, swelling and consolidations

## I. INTRODUCTION

Generally, partially saturated clayey soils having high plasticity are very sensitive to variations in water content and show excessive volume changes. Such soils, when they increase in volume because of an increase in their water contents, are classified as expansive soils. This highly plastic soil may create cracks and damage on the pavements, railways, highway embankments, roadways, building foundations, channel and reservoir linings, irrigation systems, water lines, sewer lines etc (Gromko, 1974, Mowafy, 1985 and Kehew, 1995). Thereafter, highly plastic soil exhibits undesirable engineering properties under load. They have low shear strengths and tendency to lose shear strength further upon wetting or other physical disturbances (Mitchell, 1986). Therefore, this plastic soil are very prone to shear failure due to the constant load over time and considered poor material for foundations(Liu, et. al., 2008).

Khulna is the southwest part of Bangladesh having high clayey and silt content of very soft to soft consistency up to 20 ft. from the ground surface level on the basis of several soil report collected from CRTS of Khulna University of Engineering & Technology.

*Author<sup>a</sup>* : Lecturer, Dept. of Civil Engg., Khulna University of Engineering & Technology(KUET), Khulna, Bangladesh, (Tel: +8801726703825 email: grytan\_ce04@yahoo.com)

*Author<sup>σ</sup>* : under graduate student, Dept. of Civil Engg., KUET.

*Author<sup>p</sup>* : Professor, Dept. of Civil Engg., Khulna University of Engineering & Technology, E-mail : alamgir63dr@yahoo.com

*Author<sup>σ</sup>* : Asst. Professor, Dept. of Civil Engg., Khulna University of Engineering & Technology, E-mail : rokoncekuet@yahoo.com

High water content, high compressibility and low workability of these soils often caused difficulties in the civil engineering construction projects. The soil which is used for the construction pavement or sub-base should have some specification of geotechnical properties for obtaining required strength against tensile stresses and strains variety. In this study, RHA was used for the improvement of workability, compressibility and compaction characteristics as well as the physical properties of highly plastic clayey soil. In the earlier, cement and lime are the two main materials used for stabilizing soils which is now costly in price due to the sharp increase in the cost of energy since 1970s (Neville, 2000). RHA is the most cost-effective locally available materials act as a binding agent like cement which increases some geotechnical properties as well as stabilization of soil as an alternative option of cement and lime.

Rice husk is an agricultural waste obtained from rice milling. About 108 tons of rice husks are generated annually in the world (Alhassan, 2008). In Bangladesh, about 39.3 million ton of rice is produced annually (Mustafi, 2005) which generate about 9.83 million ton of RH after milling of the paddy is used as animal food as well as fuel in rural area. RHA which is generated from the burning of Rice husk is considered as waste material and usually dumped backside of the kitchen of the village people in Bangladesh. Rice husk ash has high quantity of silica with small quantities of oxide (Agarwal, 1989, Kumar, 1993) having high specific surface that is very suitable for activating the reaction of soil and act as a binding material like cement. Thus RHA can be used as a cost-effective additive particularly in regions having high production capacity like Bangladesh. The silica content in RHA depends on the burning temperature. The technique which is used for burning RH to produce amorphous silica is suitable for pozzolana cement production, have been developed (Kumar, 1993, Ahmed, et al.1993). A mini incinerator has been designed by Ahmed, et al.(1993) in BCSIR laboratory, Dhaka to produce RHA and a comparative study has been carried out in relation to compressive strength and setting time of the pozzolana cement prepared by using this ash and boiler ash.

II. MATERIALS AND METHODS

a) Specification of Soil

Nearly greyish silty clayey soil was used in this study, collected from Khanjahan Ali Hall at Khulna University of Engineering & Technology(KUET) in Khulna, Bangladesh. The collected soils was hard and it was pulverized manually by hammer. Then the soils were screened through the sieve of 4.75 mm aperture before preparing the specimens for testing. According to the AASHTO classification systems, the soil is classified as A-7-6 and according to the Unified soil classification systems, soil is CL(Clay with low plasticity). The particle size distribution of the original soil is shown in the Figure 1.

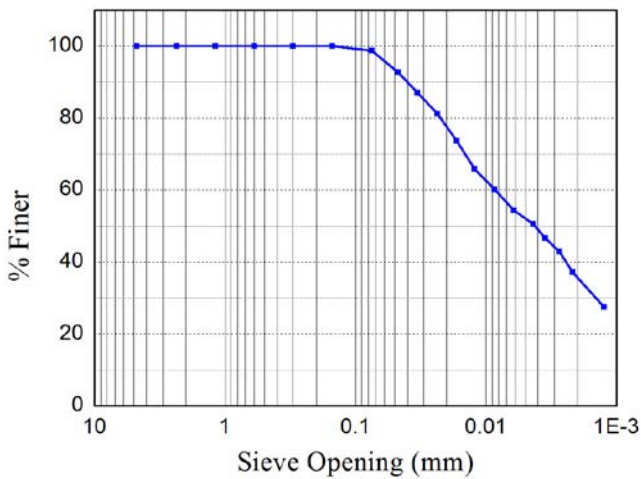


Fig 1 : Particle size distribution of original soil

b) Specification of RHA

RHA was prepared by simply burning rice husk, collected from the locally available mill. In this arrangement, rice husk were kept into a Steel box of 1.5m x 1.5m in dimensions. Five thermocouples with a connecting data logger were used for measuring the burning temperature. Briquettes were used as fuel to start and maintain fire. The produced RHA contains about 93% silica which is a key factor for improving the properties of soil.

c) Preparation of testing samples

The collected soils and ash contents were oven-dried at 105°C overnight to remove moisture and repress microbial activity. Then the oven dried samples were mixed thoroughly by hand in a large tray in a dry state as per shown in Table 1.

Table 1 : Combination scheme of soil samples

Samples ID	Samples Description		
	Soil (gm)	RHA (gm)	% Ash content
Original soil	4000	--	0
R1	4000	200	5
R2	4000	300	7.5
R3	4000	400	10
R4	4000	500	12.5

d) Testing procedure

To determine the workability, compressibility, strength and compaction characteristics of treated and original soil samples several tests were performed in the laboratory.

Before conducting the compaction test, the non-treated and RHA treated soils (5, 7.5, 10% and 12.5% RHA content) were mixed with water for about ten minutes by hand. After that, the mixtures were put into polyethylene bags and mixing was continued by shaking, overturning and pressing the bag to squeeze out the air from the soil voids. In the similar way, different amount of water contents were added to the different soil samples and mixing were done as described before to obtain the optimum moisture content and maximum dry density. A series of standard proctor tests on non-treated and RHA treated soils were conducted according to ASTM D 698.

Specific gravity of original and ash treated soil samples were determined according to ASTM D854. Consistency of the original and treated soil samples were determined by Atterberg limit test (ASTM D-4318). The effect of shrinkage of fine grained soils are of considerable significance to cause serious damage to small building and highway pavements. Free swell index of soil samples were determined as per as IS: 2720(Part-40). Ten grams of soil samples were put into two 100ml glass cylinders and the remaining volumes of the cylinders were filled with distilled water and kerosene respectively. After keeping it overnight the volume of soil in each cylinder was measured and from this volume free swell index of soil was determined from the equation shown in below.

Free swell index (%) =

$$\frac{\text{Volume of in distilled water} - \text{Volume of in distilled ker osene}}{\text{Volume of in distilled ker osene}} \times 100$$

All the test specimens for strength and consolidation tests were prepared by compacting the soils mixed with RHA (0, 5, 7.5, 10% and 12.5%) in the standard compaction molds at the corresponding optimum moisture content which has been determined already. The specimens were demolded after completion of compaction and samples of different size

were prepared as per requirement for performing the selected test in uncured condition.

The uncured unconfined compressive strength of the cylindrical specimens (36 mm diameter and 71 mm length) was determined according to ASTM D-2166. Drained shear strength parameters ( $c$  &  $\phi$ ) were determined by direct shear test (ASTM D 3080) of the compacted uncured soil specimens (60mm diameter and 25 mm height). Settlement characteristics of soils were determined by performing consolidation test (ASTM D-2435) on the samples of 63.5 mm diameter and 25 mm height.

### III. RESULTS AND DISCUSSIONS

#### a) Compaction characteristics

The variation of optimum moisture content and maximum dry density of RHA treated and untreated soil is shown in figure 2. This figure represents the maximum dry density of soil decreases gradually with an increase of RHA content. This is due to comparatively low specific gravity value (2.25) of RHA than that of replaced soil (2.65) and the initial simultaneous flocculation and agglomeration of clay particles caused by cation exchange may be the another cause. On the other hand, the optimum moisture content of soil increases with an increase RHA, because RHA are finer than the soil. The more fines the more surface area, so more water is required to provide well lubrication. The RHA content also decrease the quantity of free silt and clay fraction, forming coarser materials, which occupy larger spaces for retaining water. The increase of water content was also attributed by the pozzalanic reaction of RHA with the soil.

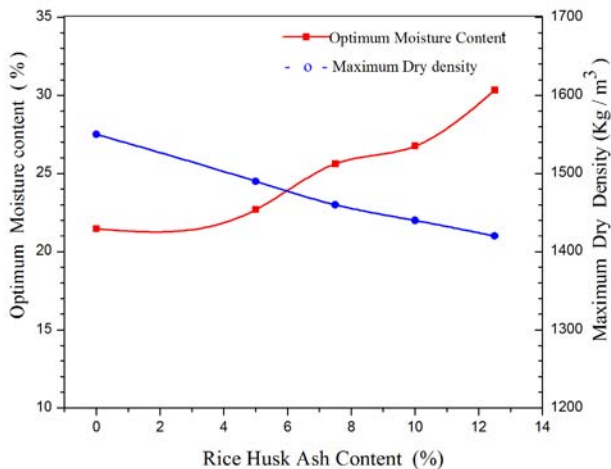


Fig 2 : Variation of maximum dry density and optimum moisture content with rice husk ash content.

The specific gravity of composite soil is decreasing due to the addition of RHA as shown in Figure 3 because of the low specific gravity of participating RHA as compared with soil.

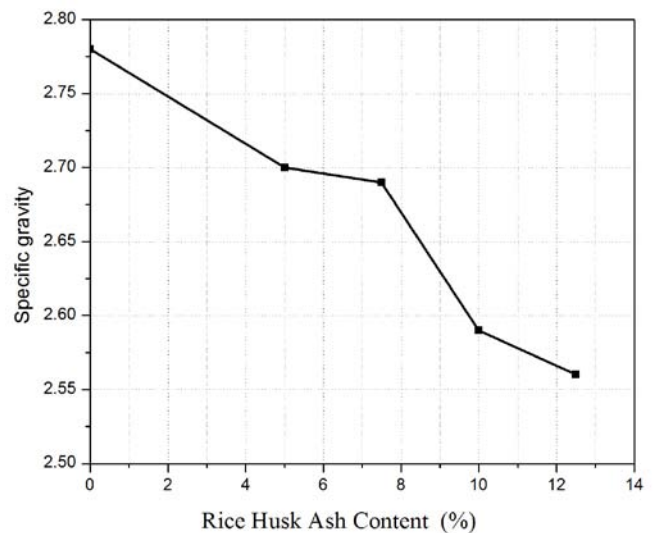


Fig 3 : Variation of specific gravity of soil with rice husk ash content.

#### b) Index Properties

Soil index properties are used extensively by engineers to discriminate between the different kinds of soil within a broad category. The index properties of soil is obtained from Atterberg limit test results and free swell index test. The Atterberg limits are a basic measure of the nature of a fine-grained soil. The test result of atterberg limit is shown in Table 2.

Table 2 : Atterberg limit test result

RHA(%)	LL(%)	PL(%)	PI(%)	SL(%)	SR
0	46	22	24	22	1.62
5	50	27	23	27	1.55
7.5	52	31	21	28	1.49
10	55	34	21	31	1.51
12.5	56	36	20	34	1.37

Figure 4 shows that liquid limit of soil increases gradually with the increases of RHA content. This improvement attributed that more water is required for the RHA treated soil to make it fluid because of the pozzalonic characteristics of RHA. Similar trend was obtained for plastic limit that the value of plastic limit increases with the increases of RHA due to the pozzalonic characteristics of RHA as shown in Figure 5. This increase of plastic limit implies that RHA treated soil required more water to change it plastic state to semisolid state. This may also improve the shear strength characteristics of soil.

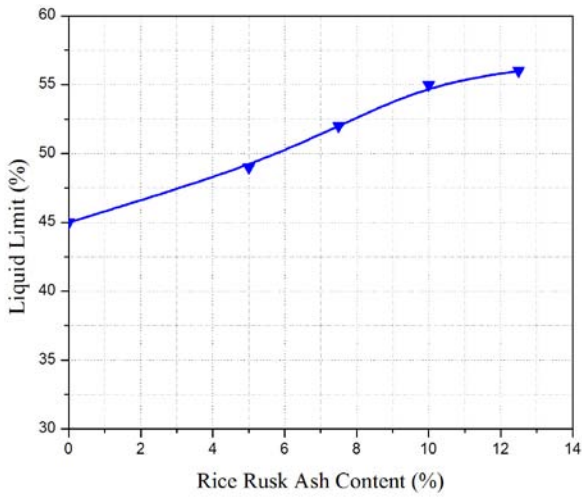


Fig 4 : Variation of LL with RHA

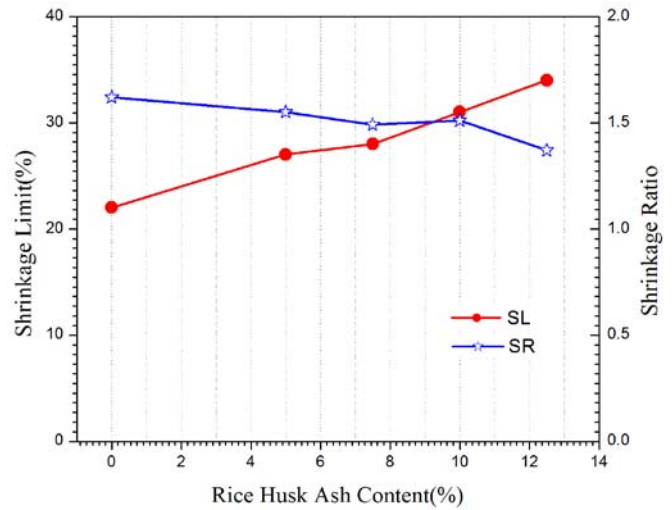


Fig 6 : Variation of Shrinkage Limit(SL) and Shrinkage Ratio(SR) with RHA

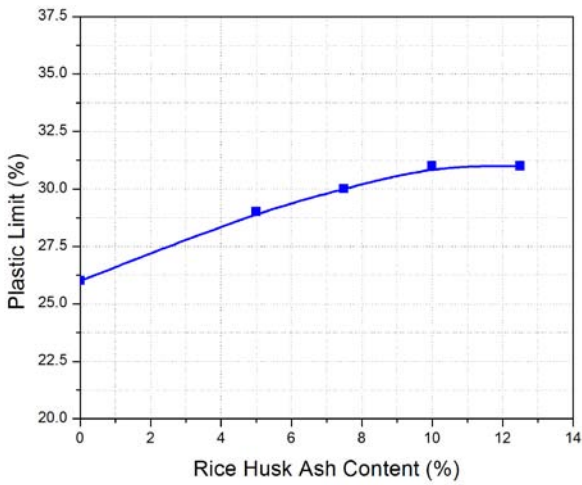


Fig 5 : Variation of PL with RHA

The shrinkage limit (SL) is the water content where further loss of moisture will not result in any more volume reduction. The variation of shrinkage limit and shrinkage ration is shown in Figure 6. Figure 6 illustrate that as the addition of RHA the value of shrinkage limit increases. It is clear from that result that the RHA treated soil absorb more water to change it semisolid state to solid state. This figure also illustrate the variation of shrinkage ratio with the RHA content. The value of shrinkage ratio decreases with the increases of RHA .

From the test result of Atterberg limit, changing of soil grain size due to the addition of RHA can be illustrated by plasticity chart. The effect of RHA on the particle size of soil is shown in Figure 7. This figure illustrate that initially the soil was clay with medium plasticity. Due to the addition of RHA, the soil class shifts to silt (due to the increase in particle sizes for the agglomeration of caly particles with RHA) and high plasticity zone. For 12.5% of RHA, it changes to silt with high plasticity.

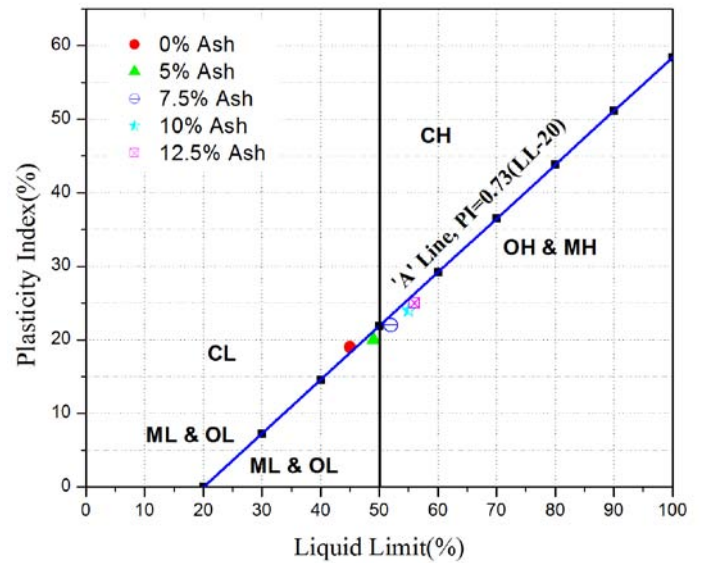


Fig 7 : Plasticity chart showing the original and RHA treated soil

The variation of free swell index with increasing RHA content is shown in Figure 8. The free swell index gradually decreased from 20% to 17.5% for up to 10% RHA content. After the addition of 2.5% more RHA content with the soil, it felt down pointedly from 17.5% to

10%. So it is clear from the above discussion that swelling of soil as well as the possibility of crack formation on foundation can be minimized with the addition of RHA.

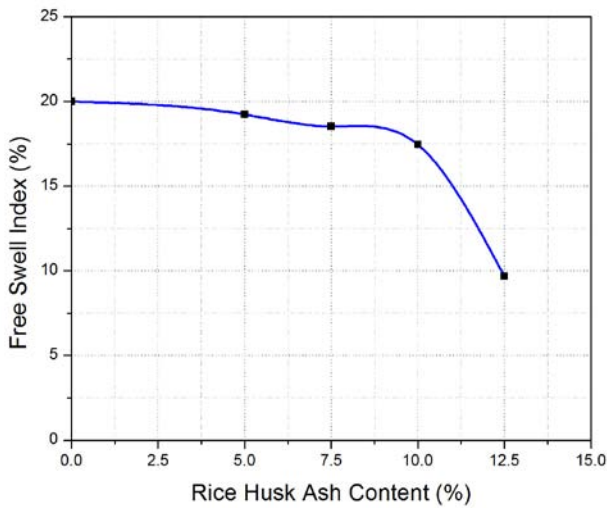


Fig 8 : Variation of Free swell index with RHA

c) Strength Characteristics

Unconfined compressive strength

The test result of unconfined compressive strength is shown in Figure 9. This figure illustrates the stress-strain behavior of original and RHA treated soil under vertical load. Initially the stress is gradually increases with the increase of strain. After attaining the peak stress, it decreases with the increase of strain for all the combination of RHA and soil. Approximately all the specimen shows shear failure after observing the failure plane of specimens. The variation of unconfined compressive strength for soil at different percentages of RHA is shown in Figure 10. There is a rapid increase of unconfined compressive strength from 0.06 MPa to 0.172 MPa with the addition of only 5% RHA. The optimum value of unconfined compressive strength 0.255 MPa were obtained for 10% of RHA content. After that, the value of unconfined compressive strength decreased from 0.255 MPa to 0.211 MPa for 12.5% of RHA content. So it can be accomplished that the maximum unconfined compressive strength were obtained at 10% of RHA and after that the value of unconfined compressive strength decreased with the addition of RHA. The following mechanism also explains that there is an positive impact of RHA on unconfined compressive strength. The reason for this improvement is due to the pozzolanic reactions of RHA with soil. This results in agglomeration in large size particles and causes the increase in compressive strength

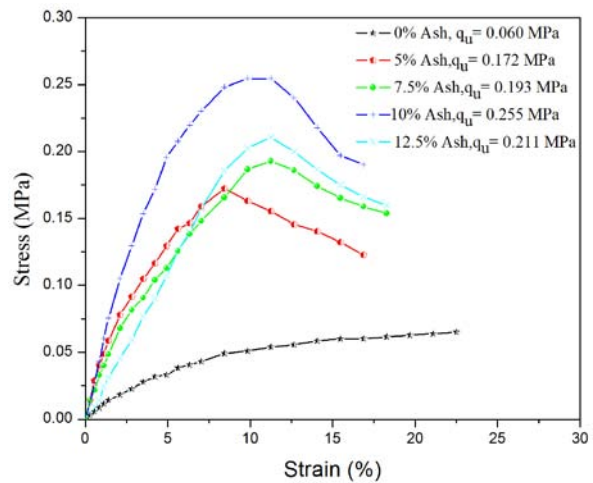


Fig 9 : UCS of original and RHA treated soil

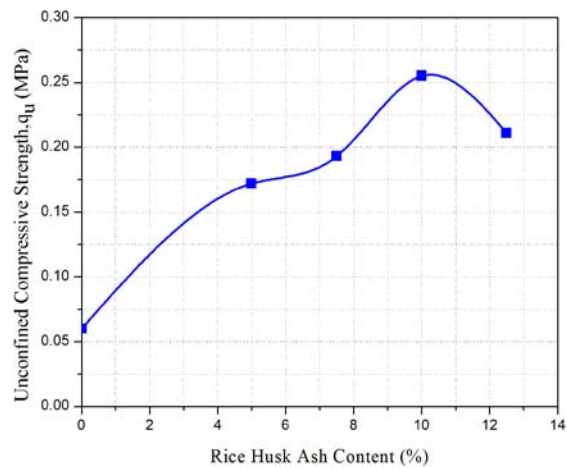


Fig 10 : Variation of UCS with RHA

Mohr-Coulomb's shear strength parameters

The Mohr-Coulomb shear strength envelopes of the RHA based composite soils are shown in the Fig. 11. Fig. 12 shows the variation of the intercept or cohesion (c) and angle or frictional angle (φ) corresponding lines. This Figure illustrates that the slope of the of curve increases with the increases of RHA and there is a rapid increase in cohesion upto 5 % of RHA content ant it decreases for the further amount of RHA content. The improvement of angle of internal friction(φ) implies that the silica content in RHA act as a binder which agglomerate the particles into a larger one and the soil changes from clay to silt. However, the 10% RHA addition gives the outermost shear strength envelope.

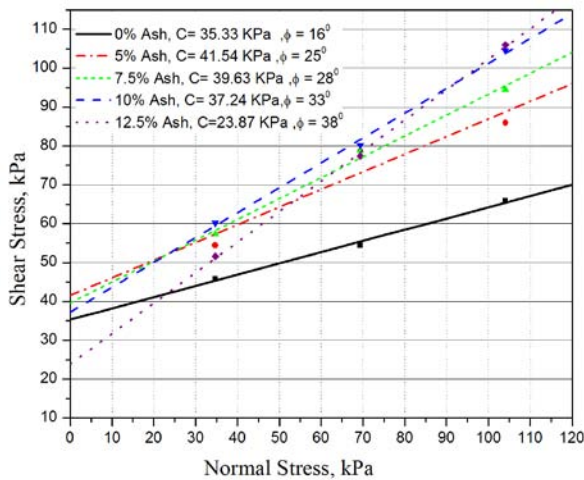


Fig 11 : Shear strength parameters(c &  $\phi$ ) of original and RHA treated soil

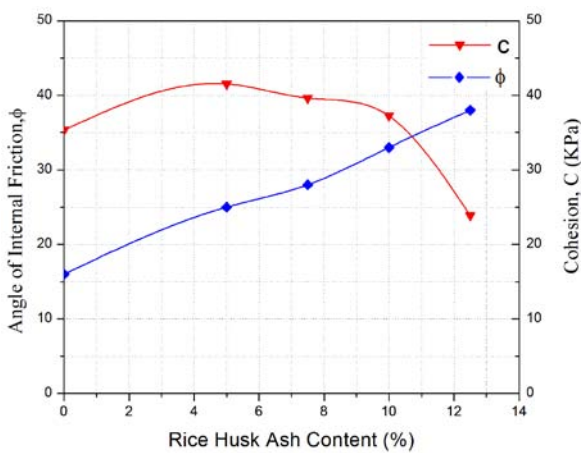


Fig 12 : Variation of shear strength parameters(c &  $\phi$ ) with RHA

d) Consolidation characteristics

In this study one dimensional consolidation test were performed to determine the consolidation characteristics of original and RHA treated soil and the corresponding consolidation curves are shown in Figure 13. The variation of compression index and initial void ratio with RHA content are shown in Figure 14. Firstly, this plot shows that the compression index ( $C_c$ ) is decreasing gradually from 0.368 to 0.328 with increasing RHA for up to 7.5%. The value of  $C_c$  decreased well under from 0.328 to 0.248 for the addition of 10% RHA with the soil and after that it is slightly increased from 0.248 to 0.258 for 12.5% RHA content. This decrease in compression index implies that there could be a result of increased formation of pozzolanic products within the pore spaces of soil from physicochemical changes (Osinubi et al. 2006) which leads to a reduction in compression index. When the rice husk ash content exceeds the quantity required for the soil-ash reaction, they will be filled between the voids

of the soil. A more compact state of the soil is probably attained. On the other hand the value of initial void ratio ( $e_o$ ) increased gradually from 1.305 to 1.378 with increasing RHA for up to 7.5%. Then the value of  $e_o$  decreased well under from 1.378 to 1.315 for the addition of 10% RHA and after that, it decreased slightly from 1.315 to 1.314 for 12.5% RHA content.

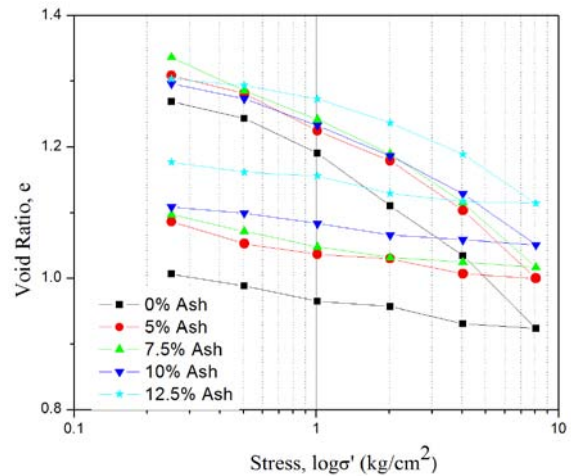


Fig 13 : Plot of void ratio,  $e$  versus effective stress,  $\sigma$

The variation of compression index and initial void ratio with RHA content are shown in Figure 14.

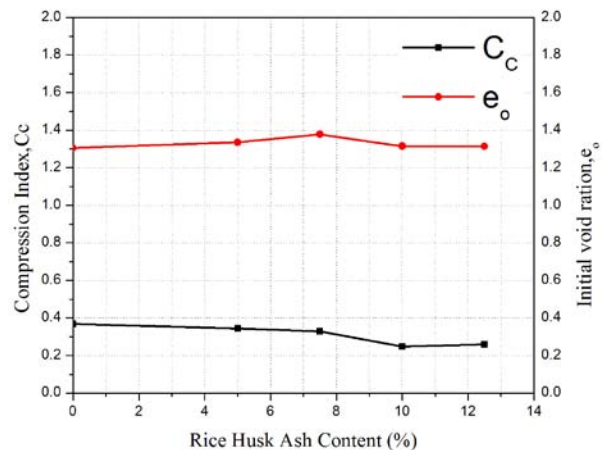


Figure 14 : Variation of Initial void ratio( $e_o$ ) and Compression index( $c_c$ ) with RHA

IV. CONCLUSIONS

In this study the effect of RHA on the geotechnical properties of cohesive soil are investigated and it can be concluded that there is an improvement of all the geotechnical properties of RHA treated soil. It was observed that the maximum dry density of soil decreased with the addition of RHA because of the lower specific gravity of RHA. The value of optimum moisture content of RHA treated soil increased because

of the pozzalonic action of RHA and soil, which needs more water. Moreover, the value of liquid limit and plastic limit also increased with the increasing percentage of RHA whereas the value of plasticity index shows different characteristics. Increasing the amount of RHA cause a decrease in shrinkage limit as well increase in shrinkage ratio which improves the shear strength characteristics of soil. The pozzalonic behavior of RHA makes the RHA treated soil coarser than original soil samples due to the agglomerations of RHA and soil particles. This improvement changes the naming of soil from clay to silt. The free swell index test result shows a negative relationship with RHA as it decreased with the increase of RHA content which reduced the possibility of crack formation on the surface of foundation. The optimum unconfined compressive strength was obtained for 10% of RHA content. The best shear strength envelope of soil was obtained for 10% of RHA. The cohesion of soil shows an increasing order for first 5 % of RHA and after that this value decreases with the addition of RHA whereas the angle of internal friction shows a positive relationship with RHA content. From the consolidation test result, it can be concluded that the values of compression index decreased with the increases of RHA and the initial void ration shows positive relation with RHA.

#### REFERENCES RÉFÉRENCES REFERENCIAS

1. Ahmed, S., Hossain, M. I. and Farooque, K. N. (1993). "Studies on rice husk ash cement." *Bang. J. Sci. Ind. Res.*, 28(2):71
2. Agrawal, B. M. (1989). "Utilization of rice husk ash." *Glass Ceram. Bull.*, **36**: 1-2.
3. Alhassan, M. (2008). "Permeability of lateritic soil treated with lime and rice husk ash." *Assumption University Journal of Thailand*, 12(2): 115–120
4. Gromko, J.G. (1974). "Expansive Soils", *Journal of the Geotechnical Engineering Division*. Vol.100, pp. 666-687.
5. Kumar, A. (1993). "Rice husk ash based cements, mineral admixture in cement and concrete, progress in cement and concrete." Ed. Ghosh, S. N. Sarker S. L. and Harsh, S. ABI Books Pvt. Ltd. CGCRI, Kolkata, India, 4:342- 367.
6. Kehew, E.A., (1995). "Geology for Engineers and Environmental Scientists." 2<sup>nd</sup> ed. Prentice Hall Englewood Cliffs, New Jersey, pp. 295-302.
7. Liu, C. and Evett, J. (2008). "Soils and Foundations." Pearson-Prentice Hall, Seventh Edition, Upper Saddle River, New Jersey
8. Mitchell, J.K. (1986). "Practical Problems from surprising soil Behavior." *J. Geotech. Eng.*, , Vol. 112, No. 3, 255-289.
9. Mowafy, Y.M. (1985). "Treatment of Expansive Soils: A laboratory Study." *Transportation Research Record* 1032, pp. 34-39.
10. Mustafi, B. A. A. (2005). "Statistical Yearbook of Bangladesh Bureau of Statistics." (BBS).
11. Neville, A M (2000). "Properties of Concrete." 4th ed. Pearson Education Asia Ltd., Kuala Lumpur, Malaysia
12. Osinubi , K. J. and Eberemu, A. O. (2006) "Effect of Bagasse Ash on the Strength of Stabilized Lateritic Soil," *Proceedings of 5th Nigerian Material Congress, Abuja*, 15-18, pp. 214-220.