



GLOBAL JOURNAL OF RESEARCHES IN ENGINEERING: A
MECHANICAL AND MECHANICS ENGINEERING
Volume 17 Issue 1 Version 1.0 Year 2017
Type: Double Blind Peer Reviewed International Research Journal
Publisher: Global Journals Inc. (USA)
Online ISSN:2249-4596 Print ISSN:0975-5861

Modeling and Experimental Analysis of Effect of Tool Geometry on Single Point Incremental Sheet Metal Forming

By Rahul Pachori & Naveen Agrawal

Mewar University

Abstract- Dieless manufacturing process involves progressive deformation of the sheet metal using a punch (or tool). During the incremental deformation process, the sheet may or may not be supported on its back side. There are various factors that affect the process of die less sheet forming. The objective of this work is to identify the effect of tool geometry on formability of sheet metal components in the case of single point incremental sheet metal forming. For this purpose numbers of experiments have been performed with three different tool geometries, which are spherical tool, elliptical tool tip with straight diameter and elliptical tool tip with tapered diameter. The entire exercise has also been simulated in virtual environment and a good correlation between the simulation and the experimental work is observed. It has been observed that the results of the analysis would help to improve the selection of appropriate tool and obtain better forming limit for a given sheet metal.

Keywords: *single point incremental sheet forming, tool geometry, wall angle, contact area, forming limit.*

GJRE-A Classification: FOR Code: 861206, 010102



Strictly as per the compliance and regulations of:



© 2017. Rahul Pachori & Naveen Agrawal. This is a research/review paper, distributed under the terms of the Creative Commons Attribution-Noncommercial 3.0 Unported License (<http://creativecommons.org/licenses/by-nc/3.0/>), permitting all non commercial use, distribution, and reproduction in any medium, provided the original work is properly cited.

Modeling and Experimental Analysis of Effect of Tool Geometry on Single Point Incremental Sheet Metal Forming

Rahul Pachori^α & Naveen Agrawal^ο

Abstract- Dieless manufacturing process involves progressive deformation of the sheet metal using a punch (or tool). During the incremental deformation process, the sheet may or may not be supported on its back side. There are various factors that affect the process of die less sheet forming. The objective of this work is to identify the effect of tool geometry on formability of sheet metal components in the case of single point incremental sheet metal forming. For this purpose numbers of experiments have been performed with three different tool geometries, which are spherical tool, elliptical tool tip with straight diameter and elliptical tool tip with tapered diameter. The entire exercise has also been simulated in virtual environment and a good correlation between the simulation and the experimental work is observed. It has been observed that the results of the analysis would help to improve the selection of appropriate tool and obtain better forming limit for a given sheet metal.

Keywords: single point incremental sheet forming, tool geometry, wall angle, contact area, forming limit.

I. INTRODUCTION

Incremental sheet metal forming is a new method, which consists of improved possibilities of sheet metal forming. Now days, incremental sheet metal forming has become very attractive method for making 3-D complex shapes. The main advantage of this process is the cost and time reduction by eliminating the making of special purpose dies. With the controlled movement of a tool; wide range of 3D shapes can be formed directly from the CAD model by moving the tool along an optimized path. This process is suitable for small batch production as well as to fabricate complex geometries [1-4].

There are several ways in which various ISF methods can be categorized. The traditional method is to define through the surface shape achieved with the process, i.e. convex surface or the concave surface. [5-6]. Incremental CNC forming technology can be used to achieve non-symmetrical shapes formed on the concave surface [7]. The convex surface forming was the first variation of ISF, known as Die less NC Forming. It was introduced in Japan by Matsubara [8].

Author α: Mechanical Engineering Discipline Mewar University, Department of Mechanical Engineering, Chittorgarh. e-mail: Rpachori2006@gmail.com

The current ISF processes can be divided in various groups, depending on the number of contact points between sheet and tool and also on the clamping mechanism. The first is the 'Single Point Incremental Sheet Forming' (SPISF), where only a single tool is used to form the component. The sheet is supported only at the edges with the clamps. Other variant is the 'Two point Incremental Sheet forming' (TPISF), where a full or partial stationary die is present to support the sheet.

The advanced variants are under research where the support die is also moving [9]. Another interesting variant under research is the ISF by hammering [10-11]. Most of the ISF configurations use the 3 axis CNC machines as the base, but new configurations based on the robotized tools are also experimented [12-13]. Kitazawa has implemented ISF using a lathe [14-15]. In order to achieve the desired accuracy in the form and dimension using ISF, it is important to know the factors influencing the process and their relationship. Several attempts have been made to investigate the behavior of the sheet metal in ISF [16-19].

In literature, many experiments on die less forming have been reported, but the effect of tool geometry on sheet metal deformation process is not well defined. Most of the experiments performed to obtain a range of wall angles in the case of sheet metal deformation use either a hemispherical or ball nose tool. In the present work, specific experiments have been carried out to achieve a range of wall angles varying from wall angle 50° to 75° with a step size of 5°, so that comparative study between three different tool geometries can be performed.

II. EXPERIMENTAL DETAILS

a) Process description and tooling setup

The usual forming strategy in ISF consists of a single forming stage where the tool traces along a sequence of contour lines with a small vertical down motion in between (Fig.1). In general for forming of sheet, a hemispherical or ball nose tool is used but to observe the effect of contact area on formability, this tool is compared with two other tools, for the same process parameters.

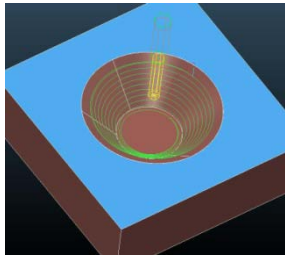


Fig. 1: Single point incremental sheet forming

In the present work, a single point incremental sheet metal forming process was performed on a CNC machining center, for three different tool geometries.

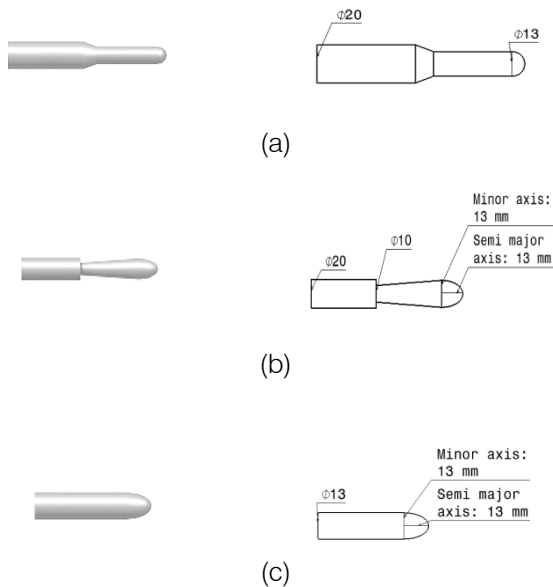


Fig. 2: Tool geometries used (a) spherical (b) elliptical with decreasing diameter (c) elliptical with straight diameter

The tool geometries are shown with the help of Fig. 2 (Fig. 2.(a) spherical, 2.(b) elliptical with decreasing diameter, 2.(c) elliptical with straight wall).

The experiments have been carried out with sheet metal specimen supported about its contour and rigidly fixed with the fixture with the help of normal clamping device [Fig. 3]. There is no lateral movement of the sheet during forming. This whole arrangement was fixed on to the worktable of the milling machine. At any instant only a small portion of the sheet is subjected to the local deformation. In the present work, tools made up of stainless steel are clamped in the spindle of the milling machine. The experiments are performed on aluminum sheets of 1 mm thickness with single point incremental sheet forming.

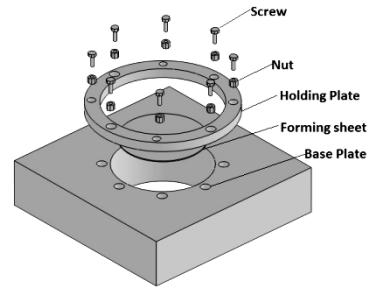


Fig. 3: Clamping mechanism of the sheet

b) Final geometry and material

Initially a disc of 200 mm diameter and 1 mm thickness is taken and we obtain symmetrical cone geometry as shown in Fig. 4. This is used to identify forming limit of sheet metal components. Due to frequent use in automobile and other sheet metal industries, Al 1050-O aluminum alloy sheets were taken for experiment.



Fig. 4: Cone shaped geometry

From the experimental observations and available literatures most influencing parameters for single point incremental sheet metal forming are listed below (Table 1). During the experiment, process parameters have been kept same; apart from wall angle and tool diameter (Fig. 5), for all the three tool geometries to obtain the comparative study.

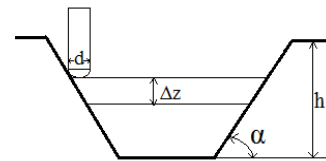


Fig. 5: Schematic view of ISF

Table 1: Process parameters

Constant	Parameters
Forming Depth "h"	80 mm
Tool Rotation	50 rpm
Feed Rate	1700 mm/min
Vertical Step Size "Δz"	0.5 mm
Tool Path	Spiral (clock wise)
Lubricant	Hydraulic oil (grade-68)
Varying	Parameters
Wall Angle "α"	50°, 55°, 60°, 65°, 70°, 75°
Tool Diameter	7, 10, 13 mm

c) The force measurements

The knowledge about the deformation force is very important for successful forming operation and to achieve final geometry precisely. It also helps in the selection of appropriate equipment.

In order to identify deformation force and to avoid tool failure the experiments have been carried out.

The force measurement set-up is shown in Fig. 6. It consists of SPISF fixture, which is mounted on the piezoelectric dynamometer. The dynamometer is also connected with the data acquisition board and a PC for output signals. The output signals have been recorded at 1000 Hz frequency for accurate results.



Fig. 6: Force measurement setup in SPISF

d) Effect of wall angle

Experiments have been carried out for wall angles of 50 to 75°, with step size of 5° and as represented in Fig. 7, which shows the effect of wall angle on maximum forming force (Fz). With other

process parameters same as in Table 1, cone geometry is formed up to 80 mm depth and actual data is plotted. To maintain the accuracy data (Force measurement) has been recorded at high frequency (1000 Hz).

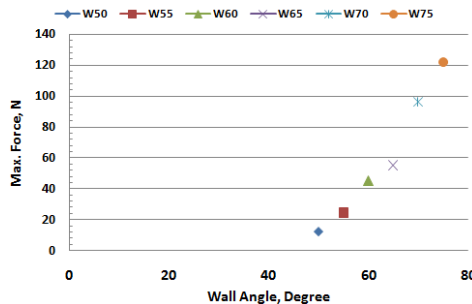


Fig. 7: Comparison of maximum forces for various wall angles

By increasing the wall angle the magnitude of maximum force occur during forming continuously increase. In case of lower wall angles (below 65° the force distribution is uniform but when wall angle exceeds 70° the force tends to increase continuously. In case of 70° wall angle, the desired depth is achieved, but in case of 75° wall angle, the fracture occurs at a depth of 14 mm only. Thus, the value of maximum force for 75° wall angle can be used to define the limit in case of SPIF for 1 mm thick aluminum sheet.

e) Effect of tool diameter

To see the effect of tool diameter on forming forces, experiments have been carried out for the wall angle of 50° and tool diameter of 7 mm, 10 mm and 13 mm respectively, with other process parameters remaining same (Table 1).

With increase in the tool diameter the value of maximum forming forces also increase (Fig. 8); this happens because the contact area between tool and sheet increases with the increase in tool diameter.

Similar results are obtained for remaining wall angles as well.

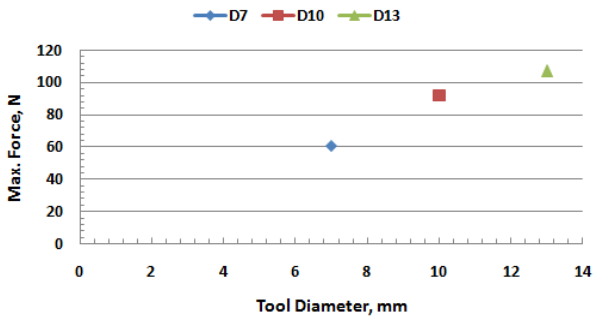


Fig. 8: Comparison of forces for different tool diameter

In case of steeper wall angle (above 70 in our case) the forming limit of specimen decreases as shown in Fig. 9. For the 7 mm tool the sheet can be formed up to 14 mm depth, whereas in case of 10 and 13 mm diameter tool forming limit is 12 and 10 mm respectively.

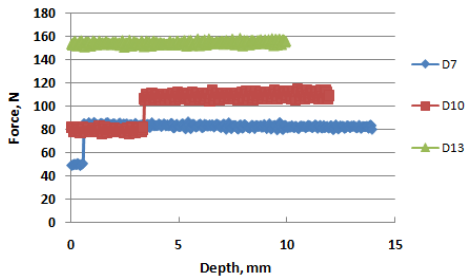


Fig. 9: Forming limit for different tool diameters

f) Comparison of different tool geometries

A set of experiments have been performed and it is observed that the maximum deformation force in case of elliptical tool tip is considerably low as compared to spherical tool tip (Fig. 10-12). The reason behind is that, in case of elliptical tool the contact area between tool and sheet is considerably low as compared to spherical one. Due to the absence of overloading the forming limit of the specimen has increased.

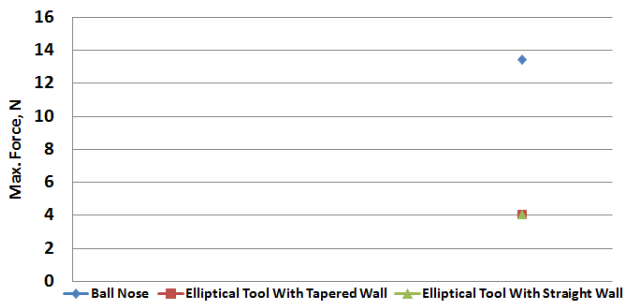


Fig.10: Comparison of maximum force for different tool geometries in case of tool diameter 7 mm and wall angle 50°

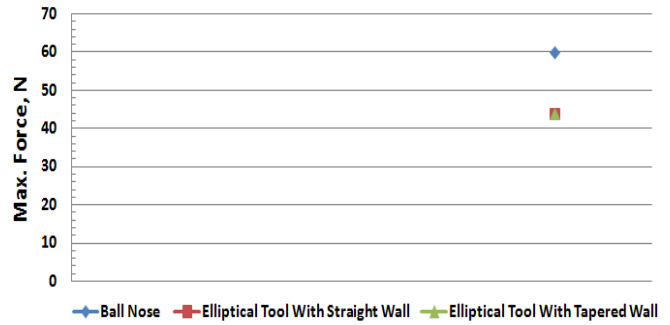


Fig.11: Comparison of maximum force for different tool geometries in case of tool diameter 10 mm and wall angle 50°

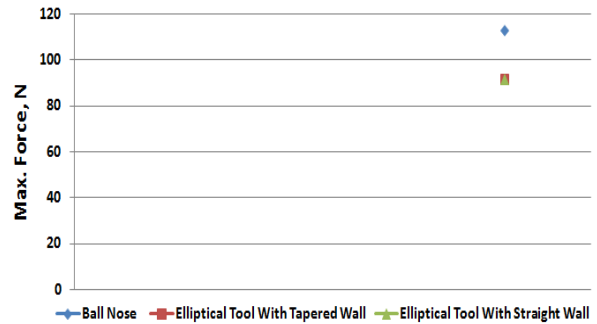


Fig.12: Comparison of maximum forces for different tool geometries in case of tool diameter 13 mm and wall angle 50°

In case of steeper wall angles (above 70 the forming limit of the component with the elliptical tool increases considerably. For 1 mm aluminum sheet forming limit in case of spherical tool is 14 mm but in case of elliptical tool with straight wall it is 19 mm and for elliptical tool with tapered wall it is 21 mm (Fig. 13).

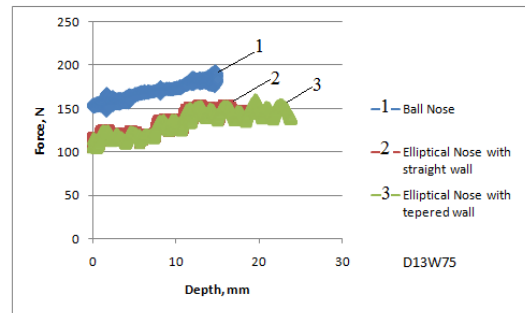


Fig.13: Forming limit for different tool geometries in case of tool diameter 13 mm and wall angle 75°

When the tool is at certain depth in case of steeper wall angles there arises a problem of collision between the tool and the wall of the sheet specimen. To overcome this problem, authors have suggested tool with tapered wall. By the graph (Fig. 13) it can be noticed that forming limit increases considerably in case of tool with tapered wall.

In the present work, contact area is calculated for both the tools in case of 50° wall angle and 0.5 mm step down (Fig. 14) for same forming depth. It is found that in case of spherical tool contact area is larger than the elliptical tool.

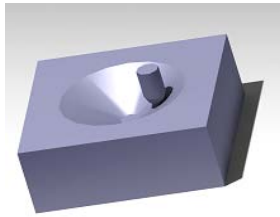


Fig.14: Tool sheet interface at 50° wall angle

As we can see that, contact area in case of spherical tool [Fig. 15 (a)] is 0.03569 m² but in case of elliptical tool [Fig. 15 (b)] contact area is 0.01813 m². Therefore, more deformation force would be transferred from tool to the sheet in case of a spherical tool and it directly affects the formability of component.

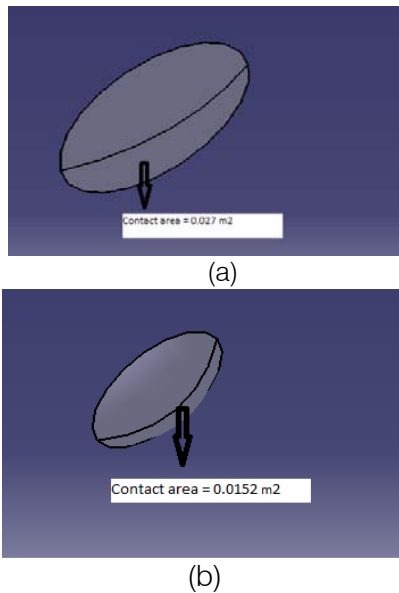



Fig.15: Contact area for (a) spherical and (b) elliptical tool

III. SIMULATION RESULTS


The single point incremental sheet forming process has been simulated in finite element analysis software, LS-DYNA. Anisotropic yield criteria, material model Hill, Bar lat and multi-linear stress-strain approaches have been employed [20]. For the tool, Solid-164 tetrahedral mesh element, and rigid body behavior and for the sheet shell-163 square element, plastic anisotropic body behavior is employed. The values of the yield stress, density, young's modulus and Poisson's ratio have been set for high carbon steel (Tool) and aluminum (sheet).

Simulations have been carried out for spherical and elliptical tools of diameter 7 mm, 10 mm and 13 mm and wall angle of 50° to 75° with a step size 5°. This work presents a case where tool diameter is of 13 mm and wall angle 50°. Same tool path as given to the CNC-milling machine is defined through array parameters in the LS-DYNA and value of maximum deformation force is identified.

Simulation results are shown with the help of Fig. 16(a) and 16(b). In case of spherical tool, the maximum force magnitude attained by the sheet is 97 N and for elliptical tool it is 86 N.

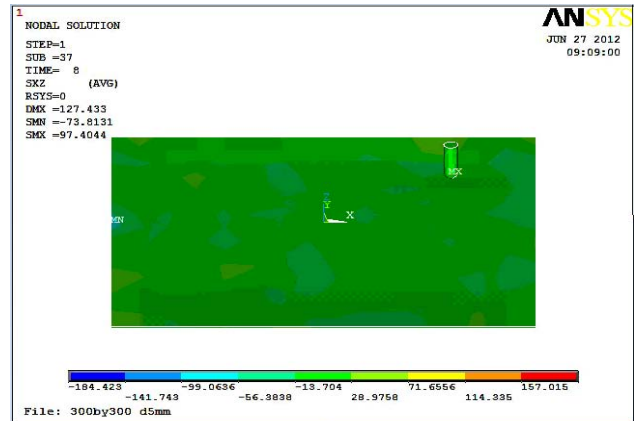

(a)

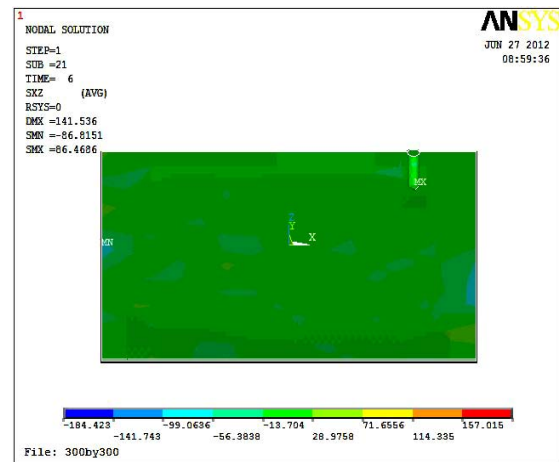

(b)

Fig.16: LS-DYNA Force (Fz) results for (a) spherical and (b) elliptical tool

As it may be seen by comparing Fig. 12 and Fig. 16 [(a), (b)], the force values are generally in agreement, except for existence of high peak value in the experimental data. These peaks may be attributed to the plunging action when the tool takes a step-down.

IV. CONCLUSIONS

A study to observe the effect of tool geometry on the formability of the component for conical shape is

performed for different tool diameters and wall angles. It is found that by changing the tool geometry from spherical to elliptical shape the forming limit of specimen increases considerably. Through the analysis, it is observed that contact area plays major role in terms of deformation force, which directly affects the forming limit of the component. In addition the elliptical tool with tapered wall gives more forming limit. Further when the tool deals with steeper wall angles the problem of tool collision with the wall of the specimen has been solved.

The ISF process is simulated in FEM LS-DYNA and by comparing experimental and simulation results, a good correlation of forces is observed.

REFERENCES RÉFÉRENCES REFERENCIAS

- Matsubara, S., "A Computer Numerically Controlled Die less Incremental Forming of a Sheet", Metal Processing Institution Mechanical Engineers, Vol. 215 Part B, 959-966, 2001.
- Filice, L., Fratini, L., Micari, F., "Analysis of Material Formability in Incremental Forming". The International Academy for Production Engineering (CIRP Annals), Vol. 51, 199-202, 2002.
- Jeswiet, J., "Incremental Single Point Forming with a Tool Post", 9th International Conference on Sheet Metal, Leuven, 37-42, 2001.
- Amino, H., Lu, Y., Ozawa, S., Fukuda, K., Maki, T., "Dieless NC Forming of Automotive Service Parts", 7th ITCP, Yokohama, 1015-1020, 2002.
- Jeswiet, J., Hagan, E., "Rapid Proto-typing of a Headlight with Sheet Metal", Proceedings of Shelmet, 165-170, 2001.
- Kim, T.J., Yang, D.Y., "Improvement of formability for the incremental sheet metal forming process", International Journal of Mechanical Sciences, Vol. 42, 1271-1286, 2001.
- Leach, D., Green, A. J., Bramley, A. N., "A new incremental sheet forming process for small batch and prototype parts", 9th International Conference on Sheet Metal, Leuven, 211-218, 2001.
- Matsubara, S., "Incremental Backward Bulge Forming of a Sheet Metal with a Hemispherical Tool", Journal of the JSTP, Vol. 35, 1311-1316, 1994.
- Franzen, V., Kwiatkowski, L., Sebastiani, G., Shankar, A. E. Tekkaya, M. Kleiner, "Dyna-Die: Towards Full Kinematic Incremental Forming", Institute of Forming Technology and Lightweight Construction (IUL), Technical University of Dortmund, baroper Street 301, 44227 Dortmund, Germany, Vol. 1, issue 1, 1163-1166, 2008.
- Schafer, T., Schraft, R.D., "Incremental Sheet Metal Forming by Industrial Robots using a hammering tool", Rapid Prototyping Journal, Vol. 11, No. 5, 278-286, 2005.
- Vihtonen, L., Puzik, A., Katajarinne, T., "Comparing Two Robot Assisted Incremental Forming Methods: Incremental Forming by Pressing and Incremental Hammering", 11th ESAFORM 2008 Conference on Material Forming: Proceedings Mini Symposia, Lyon, France, 2008.
- Callegari, M., Amodio, D., Ceretti, E., Giardini, C., "Sheet Incremental Forming: Advantages of Robotised Cells vs. CNC Machines, Industrial Robotics", Programming Simulation and Applications, 493-514, 2006.
- Meier, H., Dewald, O., Zhang, J., "A New Robot-Based Sheet Metal Forming Process", Proceedings of Shel met, 465-470, 2005.
- Kitazawa, K., Hayashi, S., Yamazaki, S., "Hemispherical stretch-expanding of aluminum sheet by computerized numerically controlled incremental forming process with two path method", Journal of Japan Institute of Light Metals, Vol. 46, 219-224, 2001.
- Kitazawa, K., Nakane, M., "Hemi-ellipsoidal stretch expanding of aluminum sheet by CNC incremental forming process with two path method", Journal of Japan Institute of Light Metals, Vol. 47, 440-445, 1997.
- Filice, L., Fratini, L., Micari, F., "Analysis of material formability in incremental forming", The International Academy for Production Engineering, Vol. 51, 199-202, 2002.
- Ceretti, E., Giardini, C., Attanasio, "Experimental and simulative results in sheet incremental forming on CNC machines", Journal of Material Processing Technology, Vol. 152, 176-184, 2004.
- Jadhav, S., "Basic Investigations of the Incremental Sheet Metal Forming Process on a CNC Milling Machine", Doctoral thesis, Dortmund University, Dortmund, 2004.
- Pohlak, M., Küttner, R., Majak, J., "Simulation of incremental forming processes of sheet metal", In Proceeding III International Conference on Advances in Production Engineering, Warsaw, Part II, 133-140, 2004
- LS-DYNA Theoretical manual, Live more software technology corporation, Livemore, 1998.